

INFLUENCE OF COMBINED HYGRO-THERMOMECHANICAL TREATMENT ON TECHNICAL CHARACTERISTICS OF POPLAR WOOD

Reza Hajihassani¹, Behbood Mohebbi^{1,}, Saeed Kazemi Najafi¹, Parviz Navi²*

ABSTRACT

Combined hygro-thermo-mechanical technique was adopted and used for densification of poplar wood instead of sole treatment. This technique is combination of two techniques of hygrothermal treatment and densification of wood. For treatment, poplar wood blocks were initially treated hygrothermally at temperatures of 130, 150 and 170°C for holding time of 20, 40 minutes. Afterwards, the densification process was carried out under a hot press (temperature 160°C for 20 minutes). For densification compression set was adjusted for 40 and 60 % based on the initial thickness (radial direction) of the blocks. The densified and non-densified wood blocks were tested for physical and mechanical properties as density, water absorption, thickness swelling, springback, bending strength, modulus of elasticity as well as shear strength parallel to grain. Results revealed that wood properties were enhanced due to the combined hygro-thermo-mechanical -treatment. According to the results, wood density was increased due to the combined hygro-thermo-mechanical -treatment significantly. The treatment improved the dimensional stability of the densified samples. It was also found that the combined hygro-thermo-mechanical -treatment could significantly improve mechanical properties and also reduce the springback in the densified poplar wood.

Keywords: Compression set, hygrothermal treatment, mechanical properties, physical properties, *Populus deltoides*, wood densification.

INTRODUCTION

Wood as a natural composite biopolymer has some unique advantages for industrial applications; such as easy access, appropriate ecological assessment, high strength/weight ratio, flexibility, easy processing, lightness, reusability, renewability, environmental compatibility, etc. Beside the advantages, it has also some disadvantages which are not all due to varying natural conditions where the trees have grown before. There are some technological limiting factors for application of the wood for structural purposes; such as moisture absorption, dimensional instability, biodegradation, photodegradation as well as weathering. Therefore, this natural material may need to be transformed in order to achieve the desired functionality (Navi and Sandberg 2011). Thermal wood modification could be a choice to achieve those goals.

Hydro- and hygro-thermal treatment of the wood are categorized as thermal wood modification techniques in aqueous medium (steam and water). Wood properties are enhanced due to those techniques according to earlier reports (Navi and Sandberg 2011). Some reports indicated that

¹Department of Wood and Paper Sciences, Faculty of Natural Resources, Tarbiat Modares University, Noor, Iran.

²Department Of Architecture, Wood and Civil Engineering, Bern University of Applied Sciences, Bern, Switzerland.

*Corresponding author: mohebbiy@modares.ac.ir

Received: 25.09.2016 Accepted: 30.10.2017

combination of hydro- and hygro-thermal treatments with other modification techniques which provides high performance properties with combination of both techniques in the wood; such CHTM and THM (Mohebbi and Sanaei 2005). The CHTM stands for combined-hydro-thermo-mechanical modification which is a method with combination of hydro-thermal wood modification and mechanical wood modification (densification) techniques (Mohebbi and Sanaei 2005) and the THM also stands for hydro-thermo-mechanical wood modification which is specified for densification of wood under water steam (Navi and Heger 2004).

Those processes are generally divided into two main groups: hydro-thermal (TH) and hydro-thermo-mechanical (THM) treatments. The TH treatment is based on water and heat, and the THM applies an additional mechanical force as well. In addition, these processes consume comparatively a little energy. The results of studies in different fields of THM/TH processes showed that wood properties; such as dimensional stability, strength, hardness and durability are improved due to the treatment (Navi and Sandberg 2011). By TH processes, the reactions related to wood chemical structure changes and hydrolysis of wood cell wall polymers carry out at elevated temperatures (160-240°C), pressures (1-3,5 MPa) and holding time from a few minutes to several hours with solid concentration below 20 wt.% (Alvira *et al.* 2010). During the TH process, hydrolysis of lignocellulosic linkages are occurred due to formation of the hydronium ions; which are generated from water hydrolysis. In other words, liquid water changes to hydronium ions at high temperatures which act as an acid and hydrolyze wood polysaccharides. The hydronium ions increase de-acetylation and hydrolysis reactions in cell wall polymers (Liu 2008). As the process is environmental friendly, there are no worries about harmful materials, corrosion of tools and also chemicals recovery (Garrote *et al.* 1999) as well as the environmental impacts. In addition to changes in the physical properties; such as dimensional stability, the hydrothermal treatment causes loss in mechanical characteristics due to reduction of wood density. It is known that the mechanical properties of wood is correlated with the density.

Wood densification is an effective mechanical modification technique to increase the density (Stamm 1964). Therefore, another new and emerging eco-friendly method has also been reported as combined of temperature, moisture and mechanical actions, which is so-called thermo-hydro-mechanical treatment (Kutnar *et al.* 2008, Mohebbi and Sanaei 2005, Inoue *et al.* 1993, Boonstra and Blomberg 2007, Navi and Girardet 2000, Navi and Heger 2004, Fukuta *et al.* 2007, Dwianto *et al.* 1999, Ito *et al.* 1998). The products manufactured by hydro-thermo-mechanical treatment have higher density and improved mechanical properties (Kutnar *et al.* 2008, Mohebbi and Sanaei 2005, Blomberg 2005, Dwianto *et al.* 1997, 1999), bioresistance (Hakkou *et al.* 2005, Boonstra *et al.* 2007), low equilibrium moisture content (Metsa-Kortelainen *et al.* 2006), improved dimensional stability (Esteves *et al.* 2007, Inoue *et al.* 1993, Hillis 1984, Hsu *et al.* 1988) and more hydrophobic effect (Mohebbi and Sanaei 2005, Tjeerdsma and Militz 2005, Welzbacher *et al.* 2008). This method is also improved wood strength and stiffness, which is suitable for species with low-densities like poplar (Mohebbi and Sanaei 2005, Gong *et al.* 2010).

Hydrothermal treatment can affect and change hydroxyl (OH) and carbonyl (C=O) groups of cellulose, hemicellulose and lignin (Popescu and Popescu 2013). Steam treatment of the wood (hydrothermal treatment) eliminates acetyl groups of the hemicelluloses by using the acetic acid production. Acidic hydrolysis of cell wall polysaccharides produce water-soluble monosaccharide (arabinose, galactose, glucose, xylose and mannose) (Ramos 2003, Lam 2011). The presence of acetic acid derived from hemicellulose is also a factor for high lignin degradation. During the hydrothermal process of softwood, destruction β -O-4 linkages in lignin structure is the main reason for reduction of wood hardness (Assor *et al.* 2009). Renovated lignin improves resistance to failure in treated samples. The modified lignin also improves treated wood resistance to water absorption (Biswas *et al.* 2011, Lam *et al.* 2011).

Effects of the densification as well as the heat treatment have been evaluated on aspen wood. Densified surface of aspen which was heat-treated at temperatures between 190-210°C had a lower density than that of those with no heat-treatment. However, the moderate density was still higher than the non-treated and non-densified wood. The thickness swelling of compressed aspen wood after heat-treatment reduced from 32 to 9% in the radial direction. The surface hardness and nail withdrawal

resistance had reduction of 33 and 37%, respectively compared with the unheat-treated densified aspen wood. The heat-treatment has also negative effect on MOE and reduces its values by 24 and 32% in densified and non-densified wood, respectively (Gong *et al.* 2010).

As above mentioned, Mohebbi *et al.* (2009) introduced the combined hydro-thermo-mechanical treatment (CHTMT). According to their report, poplar wood was initially treated hydrothermally (at temperatures of 120, 150, and 180°C for holding time of 0, 30, and 90 minutes). Afterwards, the treated samples were compressed by a hot press (160 and 180°C for 20 minutes) with a compression set of 60%. By this technique, springback was reduced in densified wood. Results also indicated that the hydrothermal treatment temperature is much more effective than that of the press temperature. Changes in chemical structure of the wood; such as hemicelluloses destruction, increased cellulose crystallinity as well as more cross-linking in lignin polymer and also hydrophobicity of the wood, hemicellulose elimination and limitation of hydroxyl groups are the reasons, for reduction of the springback, reduction of thickness swelling, increase of anti-swelling-efficiency (ASE) in CHTM-treated wood. In addition, this research showed that the CHTM-treatment increased mechanical strength (bending modulus of rupture and modulus of elasticity, impact strength and hardness) of the CHTM-treated wood.

Welzbacher *et al.* (2008) densified pine specimens at four temperatures in combination with four press times and then heat-treated the densified wood in oil at three levels of temperature for 2 and 4 hours. The compression ratio used varied from about 40 to 50%. Results showed that the densified dimension was almost completely stabilized in those specimens that were oil-treated at temperatures above 200°C.

Swelling behavior and mechanical properties of compressed Japanese cedar have been studied by Anshari *et al.* (2011). The results showed that the maximum swelling stress was in radial direction. However, in the tangential direction, the swelling stress was decreased with increasing of the compression ratio. In fact, moisture-dependent dimensional behavior was changed in the radial and tangential direction and also obtained material properties provided structural changes in wood. Moreover, by increasing of compression ratio, corresponding densities are also increased in comparison with the initial density of treated wood, which is a reason for improvement of the mechanical properties.

According to the noticed reports, there are different techniques which are used to densify wood. However, most of them had less success in reduction of springback in the densified wood. Previous work dealing with the combined-hydro-thermo-mechanical treatment showed great influence on the densified wood springback (Mohebbi and Sanaei 2005). In the current work, a similar technique has been used for densification of poplar wood. However, the densification technique was combined with the hygrothermal wood modification instead of the hydrothermal technique to understand whether this combined technique is capable of reducing the springback as well as to know any effects on mechanical properties of the densified wood.

MATERIALS AND METHODS

Wood specimens, 50×50×500 mm, were prepared from fresh flat sawn poplar wood (*Populus deltoides*) and soaked in water for 24 h prior to treatment. Afterwards, the specimens were placed in a stainless steel steaming cylinder and treated at temperatures of 130, 150, and 170°C for holding time of 20 and 40 minutes (holding time refers to the time that the specimens were treated at a constant temperature after achieving the target treatment temperature). Before the compression process and due to the high moisture content (MC) of the samples, the hygro-thermally treated samples were initially air-seasoned to reduce the moisture content and then oven-dried at temperature of 60°C to achieve MC 15%. The hygrothermally treated wood specimens were then placed in a hot press and compressed in the radial direction (thickness) at press temperatures of 160°C for 20 minutes with a compression set of 40 and 60% and the pressure 55 bar (Mohebbi and Sanaei 2005). At least 10 samples were treated for each treatment.

The mechanical (bending and shear) strength of the treated and the untreated wood samples were determined according to ASTM D 143-09 (2014). Density, water absorption, thickness swelling as well as springback of the densified and non-densified samples. The bending moduli of rupture and elasticity (with the span length/depth ratio of 15) and also shear strength parallel to grain were carried out by Dartec universal testing machine.

The water absorption and thickness swelling parameters of the oven dried samples were evaluated as follows. The specimens were soaked in water for 24, 48 and 72 h. The weight and dimensions were measured prior to and after soaking in water. The water absorption and the thickness swelling were calculated according to Equation 1 and Equation 2:

$$W_A = \frac{M_w - M_0}{M_0} \quad (1)$$

Where W_A is water absorption (%), M_w is weight after soaking in water (g) and M_0 is weight after oven-drying (g).

$$TS = \frac{T_1 - T_0}{T_0} \times 100 \quad (2)$$

Where T_s is thickness swelling (%), T_1 is thickness after soaking in water (mm) and T_0 is thickness after oven-drying (mm).

The springback of the densified specimens was immediately calculated after press (densification). Afterwards, these samples were conditioned at $25 \pm 2^\circ\text{C}$ temperature and of $65 \pm 5\%$ relative humidity for 4 weeks after densification to determine the springback once again according to Equation 3:

$$S_i = \frac{h_2 - h_1}{h_1} \times 100 \quad (3)$$

Where S_i is springback rate (%), h_1 is final thickness under press (cm) and h_2 is thickness after press and conditioning (cm).

The obtained data from the tests were statistically analyzed based on a complete randomized design (CRD) under factorial experiment and the mean values were then grouped according to Duncan's multiple range test (DMRT).

RESULTS AND DISCUSSION

Density

The hygrothermal treatment (HTT) affected the wood density in the poplar wood as shown in Figure 1. Any increase of the treatment temperature as well as the holding time reduced the wood density. Densification of the wood based on the compression sets (C.S.) of 40 and 60% has also increased the

wood density in the control samples as shown in Figure 2. The density of control samples of the poplar wood was about 0,46 g/cm³ (Figure 1); while it was 0,67 g/cm³ for the C.S. 40% and 0,85 g/cm³ m for the C.S. 60% (Figure 2). Combination of the hygrothermal treatment and the densification process (mechanical modification) (CHTMT) increased the wood density by 146% and 180% for C.S. 40% and C.S. 60%, respectively (Figure 2). In the CHTMT wood, any increase of the treatment temperature reduced the density. However, the reduction rate of the density was much less in the CHTMT wood than that of the HTT wood. The holding time has also affected the density in the CHTMT wood as shown in Figure 2. However, the rate was much less than that of the HTT wood. Similarly the density was increased by compression set (Figure 2). According to the reports, the reason for density loss in the HTT wood deals with the mass loss due to the hydrothermal treatment (Mohebbi and Sanaei 2005, Mirzaei *et al.* 2012). Here, the hygro-thermo-mechanical treatment has also showed similar action as the hydrothermal one. The reports indicated that formation of hydronium ions at high temperatures and holding time initiates hydrolysis of wood polysaccharides with following cleavage of the molecular bonds and cross-linking reactions (Liu 2008).

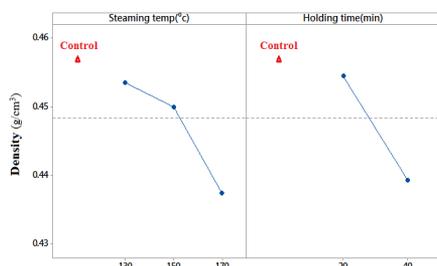


Figure 1. Main effect of hygrothermal treatment temperature and holding time on density in HTT process

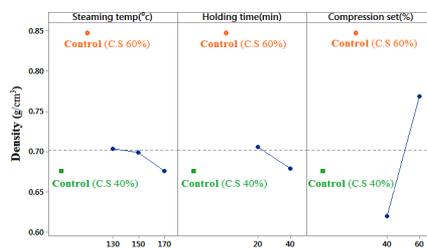


Figure 2. Main effect of hygrothermal treatment temperature, holding time and compression set on density in CHTMT process

Increasing the density due to the CHTMT is related to the densification process in wood that has caused increase of the mass vs the reduction in the wood volume. Any increase of the density in the CHTMT wood was greater than that of the non-densified control samples and the wood achieved the density of the densified control samples with the C.S. of 40% (Figure 1 and Figure 2). Mass loss due to the hygrothermal treatment might be the reason why the CHTMT wood could not achieve the C.S. of 60% in the densified control samples. The mass loss of the cell wall structures due to reactions is related to chemical changes and hydrolysis of the cell wall polymers during the hygrothermal treatment (Alvira *et al.* 2010) which are responsible for limited increase of the density by compression set.

Water absorption & Thickness swelling

As indicated in the Table 1, the treatment temperature as well as the compression set showed significant effects on the water absorption and the radial swelling of the CHTMT treated wood. However, the holding time had no significant effect on the noticed properties. There was only significant effect on the water absorption as well as the radial thickness swelling for interactions between the treatment temperature and the holding time.

Table 1. Summarized results of ANOVA for water absorption and thickness swelling in CHTM treated poplar wood.

		Water absorption (%)			Thickness swelling (%)		
		24 hours	48 hours	72 hours	24 hours	48 hours	72 hours
Main effect	T	*	**	**	*	*	*
	H	ns	ns	Ns	ns	*	*
	C	*	*	*	*	*	*
Interaction effect	T×H	*	*	*	*	*	*
	T×C	ns	ns	Ns	*	ns	ns
	H×C	ns	ns	Ns	ns	ns	ns
	T×H×C	ns	ns	Ns	ns	ns	ns

T: Hydrothermal temperature, H: Holding time, C: compression set, *: Significant at above 99% of the confidence level, **: Significant at 95% of the confidence level, ns: Insignificant

As shown in Figure 3 and Figure 4, the water absorption and the radial swelling of the CHTMT wood were reduced by increase of the treatment temperature as well as the holding time after 24 and 72 hours of soaking in water. However, the reduction for those parameters was negligible for the holding time. Any increase of the compression set caused increase of the water absorption and the radial swelling of the CHTMT and untreated densified wood as shown in Figure 3 and Figure 4. The results revealed that influence of the treatment temperature was much effective when the temperature raises from 130°C up to 170°C.

According to the results, rate of increase for the water absorption and the radial swelling are very similar for the untreated densified wood and the CHTMT treated wood when the compression set increases from 40 to 60%. However, the amount of the radial swelling for the CHTMT wood, when it is densified up to C.S. 60%, which is less than that of the untreated densified samples with the same compression set (Figure 4a and Figure 4b).

There are previous works which are indicating the dominant effect of the treatment temperature on water absorption and the swelling in comparison with the holding time (Mohebbi and Sanaei 2005). According to the reports, that has been noticed above that the temperature initiates the reactions between the cell wall polymers followed by formation of hydronium ions, cleavages and cross-linking reaction in the lignin and celluloses polymers, degradation of the hemicelluloses as well as reduction in the hydroxyl groups in the cell wall polymers (Biswas *et al.* 2011, Mohebbi and Sanaei 2005, Alvira *et al.* 2010, Navi and Sandberg 2011, Lam *et al.* 2011, Boonstra and Tjeerdsma 2006, Blomberg 2005, Navi and Girardet 2000). Therefore, they could be known as the main reasons for reduction of the water absorption and the swelling in the CHTMT treated wood. Presence of great mass per volume might be the reason for increase of the water absorption and the radial swelling in the untreated densified wood as well as the CHTMT wood samples compressed up to C.S. of 60%.

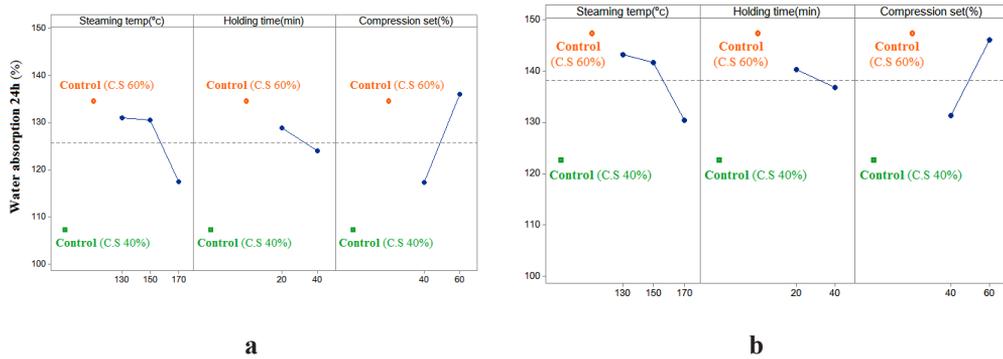


Figure 3. Effects of CHTMT treatment process parameters on radial water absorption of wood after 24h (a) and 72h (b) of soaking in water.

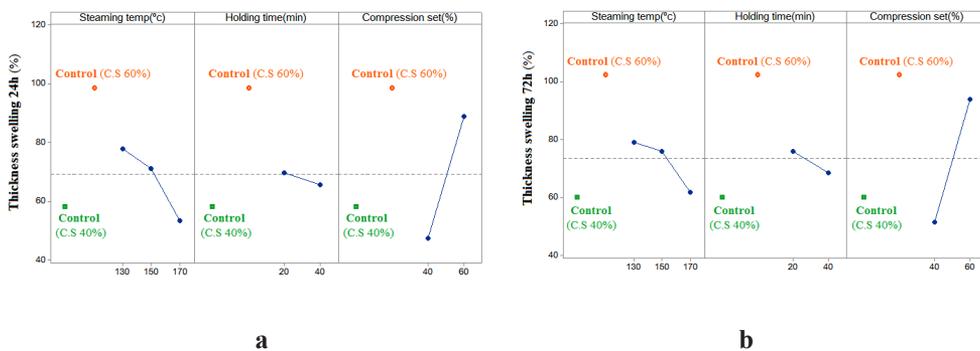


Figure 4. Effects of CHTMT treatment process parameters on radial swelling wood after 24h (a) and 72h (b) of soaking in water.

Springback

The springback of the CHTMT treated wood and the untreated densified wood was determined immediately after densification and also 4 weeks after densification. The springback of the CHTMT treated wood was reduced by the hygrothermal treatment parameters, temperature and holding time (Figure 5). As shown, influence of the treatment temperature was greater than the holding time. By increase of the compressions set, the springback was also increased in both untreated densified wood as well as the CHTMT densified samples (Figure 5). However, the amount of the springback for the CHTMT densified wood with the C.S. of 60% was less than that of the untreated samples as shown in Figure 5. It was also obtained from the results that the greater amounts of the springback were occurred immediately after the densification process (Figure 5a); while, the later springback after 4 weeks was less than that of the densification step after pressing (Figure 5b). The CHTMT wood showed less springback immediately after the pressing step; while it was great for the untreated samples (Figure 5a).

According to the results, it can be understood that the hygrothermal treatment had an effective role in springback reduction. In fact, chemical structure alteration of the wood cell wall polymers; such as hemicelluloses degradation, increased cellulose crystallinity, cross-linking in lignin structure, and also its hydrophobicity are the reasons for springback reduction according to the reports (Mohebbi and Sanaei 2005, Hakkou *et al.* 2005, Alvira *et al.* 2010, Navi and Sandberg 2011).

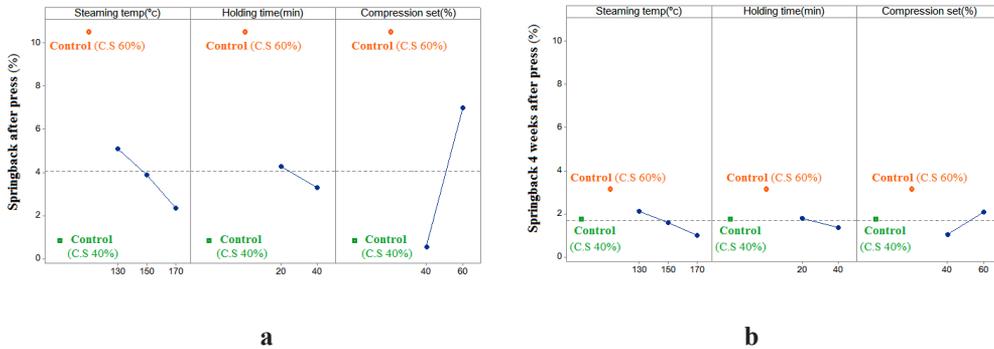


Figure 5. Effects of CHTMT treatment process parameters on springback of wood after press (a) and 4 weeks after densification (b).

Mechanical properties

MOR and MOE

Any increase of the treatment temperature as well as the holding time reduced the bending modulus of rupture in the hygrothermally treated wood (Figure 6). According to the results shown in Figure 7, densification of the untreated samples increased the MOR. However, it was not correlated with the densification amount. As shown in Figure 7, the MOR of the untreated densified wood with C.S. of 40% is more than that of the compressed one with C.S. of 60%. Anyhow, the densification increases the MOR in comparison with the control poplar samples. In the CHTMT wood, increase of the hydrothermal treatment temperature showed different effects on the MOR (Figure 7). As shown, the MOR increases up to temperature 150°C and then there is reduction at treatment temperature of 170°C. In general, for the CHTMT wood, the MOR was less than that of the untreated densified wood with C.S. of 40%. The holding time had no significant effects on the MOR for the CHTMT wood (Figure 7). Similar to the untreated densified wood, increase of the densification had reducing effect on the MOR of the CHTMT densified wood. Anyhow, the much the MOR was determined in the densified CHTMT wood as well as the untreated one in comparison with the control poplar samples (Figure 7).

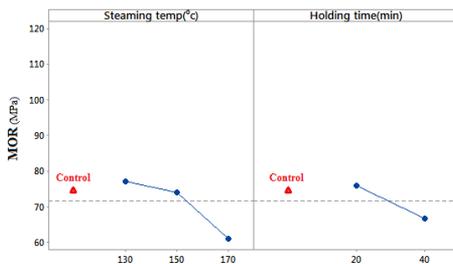


Figure 6. Main effect of hydrothermal treatment temperature on MOR in HTT process.

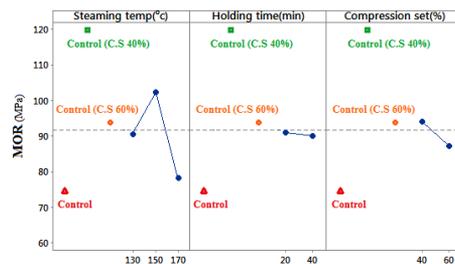


Figure 7. Main effect of hydrothermal treatment temperature on MOR in CHTMT process.

The bending modulus of the elasticity (MOE) of wood was slightly increased by the hygrothermal treatment temperature as well as the holding time in the HTT wood (Figure 8). The treatment temperature had slight varying effect on the MOE. Results revealed that the MOE was increased due to the densification process in all untreated densified wood as well as the CHTMT compressed wood in comparison with the control poplar wood samples (Figure 9). As shown, the hygrothermal treatment temperature caused increase of the MOE in the CHTMT densified wood (Figure 9). By increase of the hygrothermal treatment temperature, the MOE was increased in the CHTMT densified wood. The MOE was greater than that of the untreated densified wood with C.S. of 60% and less than that of the C.S. of 40% (Figure 9). There was a slight increasing MOE in the CHTMT densified wood due to the holding time. Increase of the compression set followed by reduction of the MOE in the CHTMT densified wood. It was similar for the untreated densified wood. As shown, the much the MOE was determined in the untreated densified wood with C.S. 40% in comparison with the C.S. 60%.

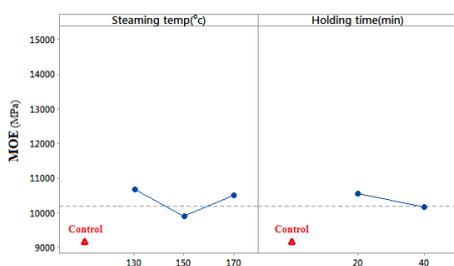


Figure 8. Main effect of hygrothermal treatment temperature on MOE in HTT process.

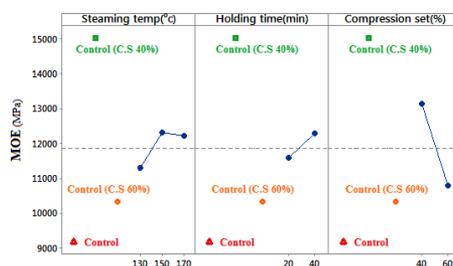


Figure 9. Main effect of hygrothermal treatment temperature on MOE in CHTMT process.

Shear strength parallel to grain

Results revealed that the shear strength parallel to grain was drastically reduced in the CHTMT densified wood samples due to the hygrothermal treatment temperature, the holding time as well as the compression set (Figure 10). In comparison with the control poplar wood samples as well as the untreated densified wood, the CHTMT wood achieved to lesser amounts of the shear strength parallel to grain. Densification of the untreated wood could increase this strength for the compression set of 40%; while there was a drastic reduction for the samples with C.S. 60% to lower than that of the control samples (Figure 10). The reduction for the CHTMT wood samples was greater than that of the untreated densified wood. It seems that densification of the wood samples in all cases had limitations for the shear strength. The severe reduction of the shear strength in the CHTMT wood might be related to brittle structure of the treated samples (Mohebbi and Sanaei 2005) which is affected by pressure force during the densification step. The brittle cell wall structures might not be able to tolerate the pressure load from the press and became crushed. As shown above, the MOE of the treated wood was increased due to the hygrothermal treatment. It means that the wood became more stiff material and it has lost its elastic property after the treatment which is not able to behave as an elastic material under press. From results above, not only increase of the densification percentages did not improve the mechanical properties in the CHTMT densified wood; but also it caused severe reduction of those properties. This might be related to less compressibility of the treated wood due to increase of the MOE. Previous works also confirmed the brittle structure of wood due to the hydrothermal or thermal wood modification processes (Mohebbi and Sanaei 2005). In fact, reduction of the mechanical properties at high temperatures is due to brittleness of the lignin polymer as well as the cleaved cellulose polymer chains (Mohebbi and Sanaei 2005).

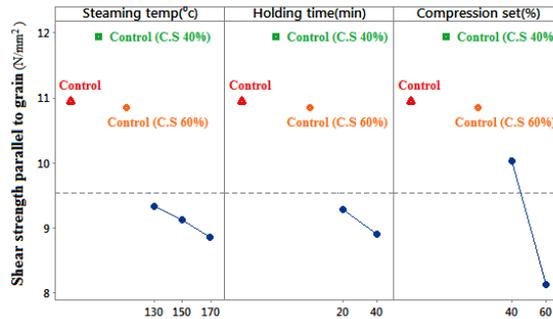


Figure 10. Main effect of compression set on shear strength parallel to grain in CHTMT process.

CONCLUSIONS

This research was aimed to study any influences of the hydrothermal treatment (HTT) as well as the hydrothermo-mechanical treatment (CHTMT) on wood properties. The following are results withdrawn from the data which were obtained in the current research work:

The hydrothermal treatment reduces the wood density; while it is increased due to the hydrothermo-mechanical process.

The CHTMT densified wood became more water repellent due to the treatment; specially the treatment temperature.

The CHTMT wood is more dimensionally stable.

The springback is reduced due to the CHTMT densification process.

The hydrothermal treatment reduces the bending modulus of rupture; while the hydrothermo-mechanical process improves this property to higher levels. However, both processing techniques increase the bending modulus of elasticity.

There is a drastic loss of the shear strength of wood for CHTMT densified wood; especially by increase of the densification.

REFERENCES

Alvira, P.; Tomas-Pejo, E.; Ballesteros, M.; Negro, M.J. 2010. Pretreatment technologies for an efficient bioethanol production process based on enzymatic hydrolysis. A Review. *Bioresour Technol* 101: 4851-4861.

Anshari, B.; Guan, Z.W.; Kitamori, A.; Jung, K.; Hassel, I.; Komatsu, K. 2011. Mechanical and moisture-dependent swelling properties of compressed japanese cedar. *Construction and Building Materials* 25: 1718-1725.

Assor, C.; Placet, V.; Chabbert, B.; Habrant, A.; Lapierre, C.; Pollet, B.; Perre, P. 2009. Concomitant changes in viscoelasticity properties and amorphous polymers during the hydrothermal treatment of hardwood and softwood. *J Agric Food Chem* 57: 6830-6837.

- American Society for Testing of Materials. ASTM. 2014.** Standard methods of testing small clear specimens of timber. ASTM D 143-09.
- Biswas, A.K.; Yang, W.; Blasiak, W. 2011.** Steam pretreatment of salix to upgrade biomass fuel for wood pellet production. *Fuel Process Technol* 92: 1711-1717.
- Blomberg, J. 2005.** Elastic strain at semi-isostatic compression of scots pine (*Pinus sylvestris*). *J Wood Sci* 51: 401-404.
- Boonstra, M.J.; Tjeerdsma, B. 2006.** Chemical analysis of heat treated softwoods. *Holz Roh Werkst* 64: 204-211.
- Boonstra, M.J.; Blomberg, J. 2007.** Semi-isostatic densification of heat-treated radiate pine. *Wood Sci Technol* 41: 607-617.
- Boonstra, M.J.; Vanacker, J.; Kegel, E.; Stevens, M. 2007.** Optimization of a two-stage heat treatment process: durability aspects. *Wood Sci Technol* 41: 31-57.
- Dwainto, W.; Inoue, M.; Norimoto, M. 1997.** Fixation of compressive deformation of wood by heat treatment. *Makuzai Gakkaishi* 43(4): 303-309.
- Dwianto, W.; Morooka, T.; Norimoto, M.; Kitajima, T. 1999.** Stress relaxation of sugi (*Cryptomeria japonica* D. Don) wood in radial compression under high temperature steam. *Holzforschung* 53: 541-546.
- Esteves, B.; Marques, A.V.; Domingos, I.; Pereira, H. 2007.** Influence of steam on the properties of pine (*Pinus pinaster*) and eucalypt (*Eucalyptus globulus*) wood. *Wood Sci Technol* 41: 193-207.
- Fukuta, S.; Takasu, Y.; Sasaki, Y.; Hirashima, Y. 2007.** Compressive deformation process of Japanese cedar (*Cryptomeria japonica*). *Wood Fiber Sci* 39: 548-555.
- Garrote, G.; Domínguez, H.; Parajó, J.C. 1999.** Hydrothermal processing of lignocellulosic materials. *Holz Roh Werkst* 57: 191-202.
- Gong, M.; Lamason, C.; LI, L. 2010.** Interactive effect of surface densification and post-heat-treatment on aspen wood. *Journal of Materials Processing Technol* 210: 293-296.
- Hakkou, M.; Pétrissans, M.; Zoulalian, A.; Gérardin, P. 2005.** Investigation of wood wettability changes during heat treatment on the basis of chemical analysis. *Polymer Degradation and Stability* 89: 1-5.
- Hillis, W.E. 1984.** High temperature and chemical effects on wood stability. Part 1: General Considerations. *Wood Sci Technol* 18: 281-293.
- Hsu, W.E.; Schwald, W.; Schwald, J.; Shields, J.A. 1988.** Chemical and physical changes required for producing dimensionally stable wood-based composites. *Wood Sci Technol* 22: 281-289.
- Inoue, M.; Norimoto, M.; Tanahashi, M.; Rowell, M.R. 1993.** Steam or heat fixation of compressed wood. *Wood Fiber Sci* 25 (3): 224-235.
- Ito, Y.; Tanahashi, M.; Shigematsu, M.; Shinoda, Y.; Ohta, C. 1998.** Compressive-molding of wood by high-pressure steam-treatment. Part 1: Development of compressively molded squares from thinning. *Holzforschung* 52: 211-216.
- Kutnar, A.; Kamke, F.A.; Petri, M.; Sernek, M. 2008.** The influence of viscoelastic thermal compression on the chemistry and surface energetics of wood. *Colloids and Surfaces A: Physicochem Eng Aspects* 329: 82-86.
- Lam, P.S. 2011.** Steam explosion of biomass to produce durable pellet. Ph.D. Dissertation, The University of British Columbia, Vancouver, Canada.
- Lam, P.S.; Sokhansanj, S.; Bi, X.; Lim, C.J.; Melin, S. 2011.** Energy input and quality of pellets

made from steam exploded douglas fir (*Pseudotsuga menziesii*). *Energy Fuel* 25: 1521-1528.

Liu, S. 2008. A kinetic model on autocatalytic reactions in woody biomass hydrolysis. *J Biobased Mater Bio* 2: 135-147.

Metsa-Kortelainen, S.; Antikainen, T.; Viitaniemi, P. 2006. The water absorption of sapwood and heartwood of scots pine and norway spruce heat-treated at 170°C, 190°C, 210°C and 230°C. *Holz Roh Werkst* 64 (3): 192-197.

Mirzaei, G.; Mohebbi, B.; Tasooji, M. 2012. The effect of hydrothermal treatment on bond shear strength of beech wood. *European Journal of Wood and Wood Products* 70: 705-709.

Mohebbi, B.; Sanaei, I. 2005. Influences of the hydro-thermal treatment on physical properties of beech wood (*Fagus orientalis*). The international research group on wood protection (IRG). 36th Annual Meeting, Bangalore, India 24 - 28 April, IRG Document No. IRG/WP 05-40303.

Mohebbi, B.; Sharifinia-Dizboni, H.; Kazemi-Najafi, S. 2009. Combined hydro-thermo-mechanical modification (CHTM) as an innovation in mechanical wood modification. In: Proceeding of 4th European Conference on Wood Modification (ECWM4). Stockholm, Sweden, 353-360.

Navi, P.; Girardet, F. 2000. Effects of thermo-hydro-mechanical treatment on the structure and properties of wood. *Holzforchung* 54: 287-293.

Navi, P.; Heger, F. 2004. Combined densification and thermo-hydro-mechanical processing of wood. *MRS Bull* 29: 332-336.

Navi, P.; Sandberg, D. 2011. Thermo-hydro-mechanical processing of wood. *Engineering Sciences* 360 p.

Popescu, C.M.; Popescu, M.C. 2013. A near infrared spectroscopic study of the structural modifications of lime (*Tilia cordata* Mill.) wood during hydro-thermal treatment. *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy* 115: 227-233.

Ramos, L.P. 2003. The chemistry involved in the steam pretreatment of lignocellulosic materials. *Quim Nova* 26: 863-871.

Stamm, A.J. 1964. *Wood and cellulose science*. New York: Ronald Press p. 549.

Tjeerdsma, B.F.; Militz, H. 2005. Chemical changes in hydrothermal treated wood. FTIR analysis of combined hydro thermal and dry heat-treated wood. *Holz Roh Werkst* 63 (2): 102-111.

Welzbacher, C.R.; Wehsener, J.; Rapp, A.O.; Haller, P. 2008. Thermo-mechanical densification combined with thermal modification of Norway spruce (*Picea abies* Karst) in industrial scale-dimensional stability and durability aspects. *Holz Roh Werkst* 66: 39-49.